

Technical Data Sheet

CAS No. 26301-10-0
9082-00-2



CARPOL[®] GSP-280

Polyether Polyol

CARPOL[®] GSP-280 is a glycerin/sucrose-initiated polyether polyol. The high functionality of the initiators yields a resultant polyol with a functionality of seven and a typical hydroxyl value of **280**. Due to this polyol's functionality, its niche is rigid foam and its applications. Blending this polyol with other polyether polyols allows for foam systems with high to low degrees of crosslinking. In addition, CARPOL[®] GSP-280 is mildly catalytic, which enables the use of less catalyst while still providing the formulator with control over the system's reactivity.


Typical End Use Applications

- Insulation
- Portable Coolers
- Pour-in-Place Insulation
- Rail Boxcars

Typical Analytical Properties*

Hydroxyl Number (mg KOH / g)	280
pH (10 parts of IPA: 6 parts of H ₂ O)	7.0
Moisture (%)	[maximum] 0.08
Color (Gardner)	[maximum] 7
Appearance	Free & Clear
Viscosity @ 25 °C (cP)	2,600
Density @ 25 °C (lb / gal)	9.22
Potassium (ppm)	[maximum] 10

Viscosity Profile

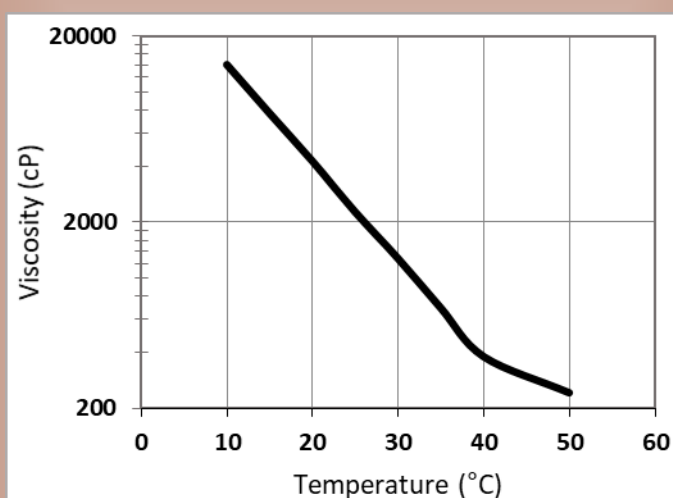

Viscosity Information

77 °F	120 °F	140 °F
2,600 cP	240 cP	200 cP

*Please note that these values are not specifications

Updated February 2019

CARPOL[®] GSP-280 Foam Formulation

<u>B-Side Components</u>	<u>Parts</u>
CARPOL [®] GSP-280	83.10
Tegostab [®] 8408	1.50
DABCO [®] R-8020	1.00
Water	2.40
Enovate [®] 245 FA	12.00

Mix Ratio

89.4 parts Polymeric MDI : 100 parts B-Side

Reactivity Profile @ 70 °C (seconds)

Cream	13
Gel	89
Free Rise	131
Tack Free	137

Physical Properties

Free Rise Density (lb / in ³)	1.75
Compression Strength, parallel (psi)	20
Compression Strength, perpendicular (psi)	21
Humid Age, 28 days, 90% Rel. Humidity, 158 °F (% Change)	-0.22
Low Temperature Age, 28 days, -20 °F (% Change)	-0.22
Oven Age, 28 days, 200 °F (% Change)	-0.31

Storage Information

CARPOL[®] GSP-280 will absorb water if the product container is not secured properly. This may affect reactivity, appearance, and performance. Therefore, it is advised that all receptacles containing this material be tightly fastened and stored in a dry place.

Consult the Safety Data Sheet for additional information.

Health and Safety Information

Health and safety information is available in the form of a Safety Data Sheet. This literature, describing proper precautions and personal protective gear, is available for review. To receive this information please contact a Carpenter Co. representative.

Ordering and Shipping Options

Sample Sizes

1 quart
1 gallon
5 gallon

Products Packaged/Shipped

Drum 460 lb net wt.
Totebin 2,300 lb net wt.
Tankwagon 40,000-45,000 lb net wt.
Railcar 185,000-189,000 lb net wt.

For additional information please contact:

Carpenter Co.
Chemicals Division
Customer Service 800-260-5373
5016 Monument Avenue
Richmond VA 23230

Updated 10 Feb 2019

Important: The information contained in this product data sheet is offered for your consideration, investigation, and verification. The data is presented in good faith and is believed to be reliable. Carpenter, however, makes no representation as to the completeness or accuracy. Carpenter makes no warranty, express or implied, with respect to the data contained herein. Carpenter cannot anticipate all conditions under which this data and the product may be used. The conditions of handling, storage, use, and disposal of the product are beyond Carpenter's control. Thus we expressly disclaim responsibility or liability for any loss, damage, or expense arising out of reliance on the information contained herein. You are advised to make your own determination as to safety, suitability, and appropriate manner of handling, storage, use, and disposal. For further information please consult the appropriate Carpenter Safety Data Sheet. **Warning:** These products can be used to prepare a variety of polyurethane products. Polyurethanes are organic materials and must be considered combustible.